


## CL 100NB Nickel-based alloy

Nickel-based alloy powder (Inconel 718), chemical composition according to ASTM B 637 UNS 07718

CL 100NB is a nickel-based alloy for the production of components for high-temperature applications.



### CHEMICAL COMPOSITION

Component	Indicative value (%)
<u>N</u>	<u>50,0 – 55,0</u>
<u>Cr</u>	<u>17,0 – 21,0</u>
<u>Nb</u>	<u>4,75 – 5,50</u>
<u>Mo</u>	<u>2,80 – 3,30</u>
<u>T</u>	<u>0,65 – 1,15</u>
<u>A</u>	<u>0,20 – 0,80</u>
<u>Co</u>	<u>0,0 – 1,0</u>
<u>C</u>	<u>0,0 – 0,08</u>
<u>Mn</u>	<u>0,00 – 0,35</u>
<u>Si</u>	<u>0,00 – 0,35</u>
<u>P</u>	<u>0,000 – 0,015</u>
<u>S</u>	<u>0,000 – 0,015</u>
<u>B</u>	<u>0,000 – 0,006</u>
<u>Cu</u>	<u>0 – 0,3</u>



## RANGE OF APPLICATION

Parts for high-temperature applications. Typical applications are turbine construction (aviation or stationary turbines) or exhaust tracts within motor sports applications.

## TECHNICAL DATA AFTER RECOMMENDED HEAT TREATMENT

Yield point $R_{p0,2}$ <sup>1</sup>	1000 – 1100 N/mm <sup>2</sup>
Tensile Strength $R_m$ <sup>1</sup>	1250 – 1350 N/mm <sup>2</sup>
Elongation A <sup>1</sup>	8 – 12 %
Young's modulus <sup>1</sup>	approx. 200.000 N/mm <sup>2</sup>
Thermal conductivity $\lambda$ <sup>2</sup>	approx. 12 W/mK
Coefficient of thermal expansion <sup>2</sup>	approx. $13 \cdot 10^{-6} K^{-1}$

<sup>1</sup> Tensile test at 20°C according to DIN EN 50125.

<sup>2</sup> Specification according to the material manufacturer's data sheet.


## CL 100NB Nickel-based alloy

## MICROSECTION

Testpiece  
(x 20 magnification)



Testpiece  
(x 100 magnification)

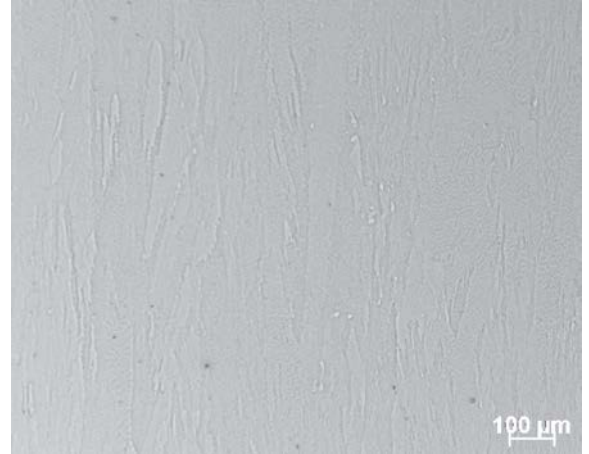

## HEAT TREATMENT

Perform heat treatment under an argon atmosphere in two steps:

At first solution annealing (980°C for one hour), afterwards allow the components to cool in the oven.

In the second step aging (720°C for 8 hours).

After this procedure allow the component to cool down to 620°C within two hours. Afterwards maintain this temperature for further 8 hours.

**EDMIT Industries Inc.**  
1400 Boulevard Ford,  
Chateauguay,  
Quebec,  
Canada, J6J 4Z2

customerservice@edmitinc.com  
T: 1-450-691-0111 ext 225  
F: 1-855-631-0365

## MICROSTRUCTURE

Components made from nickel-based alloy CL 100NB display a homogeneous, dense structure after they are manufactured by means of the metal laser melting process.

All of the specified figures are approximate figures. The figures which are provided reflect the current level of our knowledge and are dependent on process and machine parameters. The information provided on this material data sheet is therefore not binding and is not deemed to be certified.

innovation group