

Corning® EAGLE²⁰⁰⁰™

AMLCD Glass Substrates

Material Information



Display
Technologies

MIE 201

Issued: April 2005

Supercedes: November 2004

Glass Type – Alkaline Earth Boro-Aluminosilicate
Forms Available – Fusion drawn sheet
Principal Uses – Substrates for Active Matrix flat panel displays

Properties

Where applicable, units are stated in Metric and English

Mechanical

	Metric	English
Density (20°C, 68°F)	2.37 g/cm ³	147.9 lb/ft ³
Young's Modulus	70.9 GPa	10.3 Mpsi
Poisson's Ratio	0.23	0.23
Shear Modulus	28.9 GPa	4.2 Mpsi

Vickers Hardness
(200 gm load, 25 sec dwell) 642

Thermal Expansion

	Metric	English
0 - 300°C	31.8 x 10 ⁻⁷ /°C (0 - 300°C)	17.7 x 10 ⁻⁷ /°F (32 - 572°F)
Room Temperature To Setting Point	36.1 x 10 ⁻⁷ /°C (25 - 670°C)	20.1 x 10 ⁻⁷ /°F (77 - 1238°F)

Thermal Conductivity

Thermal Conductivity is a calculated value, and is equal to the product of the Thermal diffusivity multiplied by Specific Heat multiplied by Density of the glass.

Temp (°C)	Specific Heat (cal/gm-°K)	Thermal Diffusivity (cm ² /sec)	Thermal Conductivity (cal-cm/cm ² -sec-°K)
23	0.176	0.00511	0.00213
50	0.185	0.00512	0.00225
100	0.201	0.00510	0.00244
200	0.226	0.00507	0.00272
300	0.244	0.00503	0.00291
400	0.260	0.00499	0.00307
600	0.288	0.00507	0.00344


Viscosity

Working Point (10 ⁴ poises)	1321°C	2410°F
Softening Point (10 ^{7.6} poises)	985°C	1805°F
Annealing Point (10 ¹³ poises)	722°C	1332°F
Strain Point (10 ^{14.5} poises)	666°C	1231°F


Electrical

Log₁₀ Volume Resistivity (ohm-cm)

12.5	(250°C, 482°F)
10.5	(350°C, 662°F)
8.5	(500°C, 932°F)

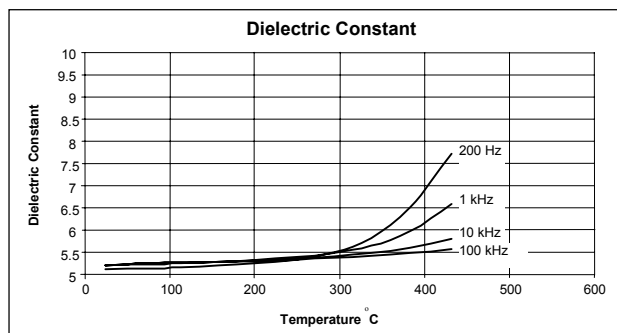

Dielectric Constant: 5.181
(20°C/68°F – 1 kHz)

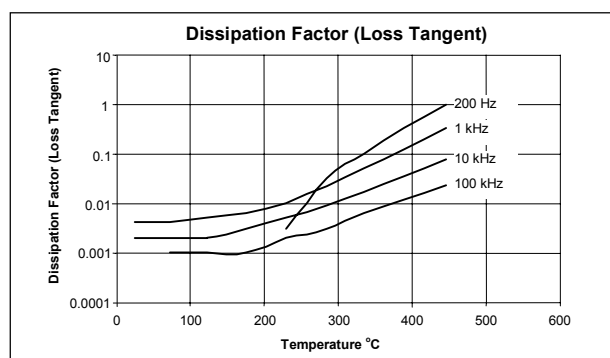

Loss Tangent: 0.40%
(20°C/68°F – 1 kHz)

Chemical

Weathering: 1

Weathering is defined as corrosion by atmospheric-borne gases and vapor such as water and carbon dioxide. Glasses rated 1 will almost never show weathering effects, those rated 2 will occasionally be troublesome, particularly if weathering products cannot be removed, those rated 3 require more careful consideration.

Durability:

Durability is measured via weight loss per surface area after immersion. Values are highly dependent upon actual testing conditions. Data is reported for EAGLE²⁰⁰⁰ and Corning 1737 glasses run concurrently. Unless otherwise noted, concentrations refer to weight percent.

Reagent	Time	Temp	Weight Loss (mg/cm ²)	
			EAGLE ²⁰⁰⁰	Corning 1737
HCl – 5%	24 hrs	95°C	0.30	0.46
HNO ₃ – 1M	24 hrs	95°C	0.17	0.24
HF – 10%	20 min	22°C	3.71	6.34
NH ₄ F:HF – 10%	20 min	22°C	0.75	1.17
1HF:10HNO ₃	3 min	25°C	1.35	2.01
1HF:100HNO ₃	3 min	25°C	0.40	0.46
DI H ₂ O	24 hrs	95°C	0.00	0.01
Na ₂ CO ₃ – 0.02N	6 hrs	95°C	0.14	0.17
NaOH – 5%	6 hrs	95°C	1.61	1.76




Total alkali content is approximately: 0.1 wt%
(Typical < 0.05 wt%)

Optical Wavelength	Refractive Index
435.8 nm	1.5170
480 nm	1.5131
486.1 nm	1.5126
546.1 nm	1.5090
589.3 nm	1.5068
643.8 nm	1.5050
656.3 nm	1.5046

Birefringence Constant

327 (nm/cm)/(kg/mm²)

Transmittance

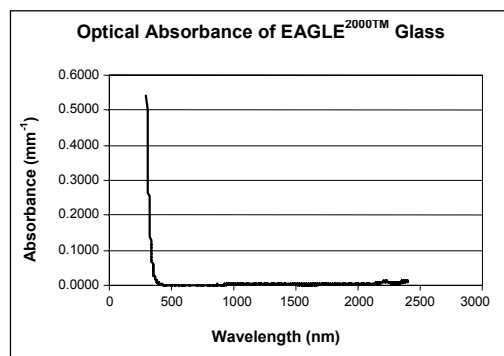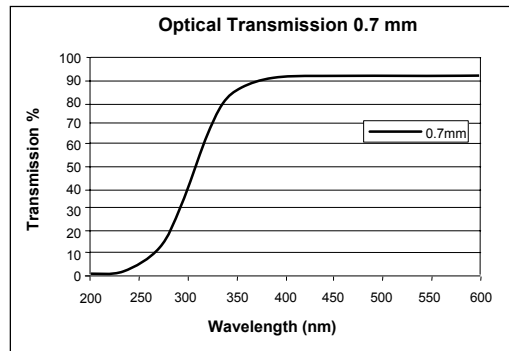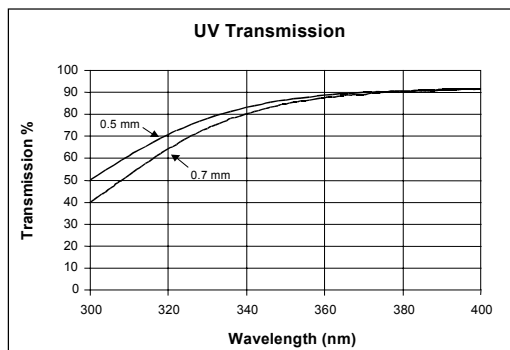

North America and all other Countries
Corning Display Technologies
 MP-HQ-W1
 Corning, NY 14831
 United States
 Telephone: +1 607-974-9000
 Fax: +1 607-974-7097
 Internet: www.corning.com/displaytechnologies

Japan
Corning Japan K.K.
 Main Office
 No. 35 Kowa Building, 1st Floor
 1-14-14, Akasaka
 Minato-Ku, Tokyo 107-0052 Japan
 Telephone: +81 3-5562-2260
 Fax: +81 3-5562-2263
 Internet: www.corning.co.jp

Nagoya Sales Office
 Nagoya Bldg., 7 F
 4-6-18, Mei-eki, Nakamura-ku
 Nagoya-shi, Aichi 450-0002 Japan
 Telephone: +81 52-561-0341
 Fax: +81 52-561-0348

China
Corning (China) Ltd., Shanghai Representative Office
 31/F, The Center
 989 Chang Le Road
 Shanghai 200031
 P.R. China
 Telephone: +86 21-5467-4666
 Fax: +86 21-5407-5899

Taiwan
Corning Display Technologies Taiwan Co., Ltd.
 Room #1203, 12F, No. 205
 Tun Hua North Road,
 Taipei 105, Taiwan
 Telephone: +886 2-2716-0338
 Fax: +886 2-2716-0339
 Internet: www.corning.com.tw

Korea
Samsung Corning Precision Glass Co., Ltd.
 20th Floor, Glass Tower Building
 946-1 Daeche-Dong
 Kangnam-Ku, Seoul 135-708
 Korea
 Telephone: +82 2-3457-9846
 Fax: +82 2-3457-9888
 Internet: www.samsungcp.co.kr

EAGLE 2000 is a trademark of Corning Incorporated, Corning, N.Y.
 ©2005, Corning Incorporated